

See discussions, stats, and author profiles for this publication at: <https://www.researchgate.net/publication/320078132>

# Epoxidized Palm Oil Plasticized Polycaprolactone Nanocomposites Preparation

Article in Nano Biomedicine and Engineering · January 2017

DOI: 10.5101/nbe.v9i3.p214-220

CITATIONS

7

READS

148

13 authors, including:



[Ali Abdulabbas](#)

Al-Furat Al-Awsat Technical University

18 PUBLICATIONS 129 CITATIONS

[SEE PROFILE](#)



[Ahmed Ghanim Wadday](#)

Al-Furat Al-Awsat Technical University

42 PUBLICATIONS 40 CITATIONS

[SEE PROFILE](#)



[Sabah Mohammed Al-Mutoki](#)

Al-Furat Al-Awsat Technical University

13 PUBLICATIONS 40 CITATIONS

[SEE PROFILE](#)



[Zaidoon Jawad](#)

University of Misan

14 PUBLICATIONS 32 CITATIONS

[SEE PROFILE](#)

Some of the authors of this publication are also working on these related projects:



Al/PANI-MWNT/Au-Plastic Schottky Diode Solar Cells [View project](#)



This paper presents an study of Channel effects on MAES ciphering algorithm. An encrypted image by MAES is transmitted and received over WiMAX standard then check its features [View project](#)



Research Article

# Epoxidized Palm Oil Plasticized Polycaprolactone Nanocomposites Preparation

Emad Abbas Jaffar Al-Mulla<sup>1</sup>✉, Fayq Hsan Jabbar<sup>2</sup>, Zaidoon Jawad Kadhim<sup>3</sup>  
Ali Abdulabbas Abdullah<sup>4</sup>, Ahmed Ghanim Wadday<sup>4</sup>, Sabah Mohammed Mlkat<sup>5</sup>

<sup>1</sup>Department Pathological Analysis, College of Health and Medical Techniques, Al-Furat Al-Awsat Technical University, 54003 Al-Kufa, Iraq.

<sup>2</sup>Department of Research and Development, Alkarkh University of Science, Baghdad, Iraq.

<sup>3</sup>Department of Chemistry, College of Science, University of Missan, Iraq.

<sup>4</sup>Engineering Technical Faculty, Al-Furat Al-Awsat Technical University, An-Najaf, Iraq.

<sup>5</sup>Electrical Department, Al-Furat Al-Awsat University, Technical Institute of Samawa, Samawa, Iraq.

✉ Corresponding author. E-mail: almullaemad@gmail.com

**Received:** Aug. 15, 2017; **Accepted:** Sep. 14, 2017; **Published:** Sep. 20, 2017.

**Citation:** Emad Abbas Jaffar Al-Mulla, Fayq Hsan Jabbar, Zaidoon Jawad Kadhim, Ali Abdulabbas Abdullah, Ahmed Ghanim Wadday, Sabah Mohammed Mlkat, Epoxidized Palm Oil Plasticized Polycaprolactone Nanocomposites Preparation. *Nano Biomed. Eng.*, 2017, 9(3): 214-220.

**DOI:** 10.5101/nbe.v9i3.p214-220.

## Abstract

As alternatives to petroleum-based polymeric materials, biodegradable polymers, such as polycaprolactone has attracted a lot of attention in the scientific community due to a rapid growth of intensive interest in the global environment. Chalcone, hexadecylamine and tetradecylamine were used as one of the organic compounds to modify natural montmorillonite clay. The clay modification was carried out by stirring the clay particles in an aqueous solution of chalcone-montmorillonite, hexadecylamine-montmorillonite and tetradecylamine-montmorillonite increasing from 1.29 to 1.53, 1.59 and 1.79 nm, respectively. The modified clay was then used in the preparation of the polycaprolactone/epoxidized palm oil blend nanocomposites. They were prepared by incorporating 0.5-5% of chalcone-montmorillonite, hexadecylamine-montmorillonite and tetradecylamine-montmorillonite. The interaction of the modifier in the clay layer was characterized by X-ray diffraction and transmission electron microscopy. The nanocomposites were synthesized by solution casting of the modified clay and a polycaprolactone/epoxidized palm oil blend at the weight ratio of 80/20, which had the highest increase in the tensile strength of the blend. The X-ray diffraction and transmission electron microscopy results confirmed the production of nanocomposites. The results also showed higher thermal stability for nanocomposites compared to those of the polycaprolactone/epoxidized palm oil blend.

**Keywords:** Nanocomposites; Surfactants; Organic cations; MMT; PCL; EPO

## Introduction

The polycaprolactone (PCL) appears to be most attractive because of its availability and biodegradability [1, 2]. Many efforts have been made to discover, develop and modify biodegradable

polymers derived from renewable resources [3].

The PCL is one of the biodegradable thermoplastic polyesters which can be prepared from butanediol and succinic acid produced by fermentation process [4, 5]. In addition to its applications in textile industry and medical fields, PCL is a promising candidate

to produce disposable packaging. However, low molecular weight, low stiffness and high cost restrict its applications [6]. Many studies have been conducted to enhance the properties by blending biodegradable polymers with other polymers or using low molecular weight plasticizers [7-13]. The morphologies and phase behaviors of polylactic acid / PCL blend have been investigated [14].

The epoxidized palm oil (EPO) is used to improve properties and biodegradation of PCL. EPO is produced from esters of glycerol in palm oil containing different saturated and unsaturated fatty acids. It offers many advantages in chemical industries field because it is derived from renewable, biodegradable and abundant raw materials [9, 16-18]. The incorporation of organoclays in the polymer to produce a nanocomposite is another means to modify the property balance of a material. The improvements in thermal stability, physical and mechanical properties can be achieved by addition of 0.5-5% weight of organoclays in comparison to the neat polymer [19, 20].

The montmorillonite (MMT) modification may carry out by exchanging the original interlayer cations of organic cations where they are transformed from organophobic to organophilic materials and significantly increase the basal spacing of the clay layers [21]. It is generally accepted that the extent of swelling depends on the length of the alkyl chain and the cationexchange capacity of the clay [22].

Organoclays are mainly obtained by exchanging cations in the clay minerals, which contain hydrated  $\text{Na}^+$  ions with alkylammonium [23, 24]. It is reported that the organo-modified MMT-based composites have shown the possible competition between the polymer matrix and the plasticizer for the intercalation between the aluminosilicate layers [25].

In the present study, chalcone (CH), hexadecylamine (HAD) and tetradecylamine (TDA), as ammonium compounds, were used to modify the compatibility of

MMT clay with EPO plasticized polycaprolactone to produce nanocomposites.

## Experimental Materials


MMT, HAD and TDA were obtained from Sigma Aldrich, Germany. EPO was provided by Advanced Oleochemical Technology Division (AOTD), Malaysia. PCL and chloroform were purchased through local suppliers from Nagoya, Japan and Merck, Germany, respectively. P-aminoacetophenone and p-chlorobenzaldehyde were obtained from Fluka, Germany. Sodium hydroxide and hydrochloric acid were obtain from J.T. Baker, USA.

## Methods

**Preparation of Chalcone (CH)** was carried out according to procedure described by Sadiq et al., 2015 [26].

### Preparation of organoclay

Organoclay was prepared with a cationic exchange process, where  $\text{Na}^+$  in the MMT was exchanged with alkylammonium ion from CH, HDA and TDA, which was reported in our previous paper [27], in an aqueous solution. 4.00 g of MMT was stirred vigorously in 600 mL of hot distilled water for 1 h to form a clay suspension. Subsequently, a designated amount of CH, HDA and TDA compounds, which had been dissolved in 400 mL of hot water and the desired amount of concentrated hydrochloric acid (HCl) was added into the clay suspension of CH, HDA and TDA compounds. After being stirred vigorously for 1 h at 80 °C, the organoclay suspension was filtered and washed with distilled water until no chloride was detected with 1 mol silver nitrate solution. It was then dried at 60 °C for 72 h. The dried organoclay was ground until the particle size was less than 100  $\mu\text{m}$  before the preparation of the nanocomposite. Scheme 1 is the schematic drawing of the nanocomposites production.

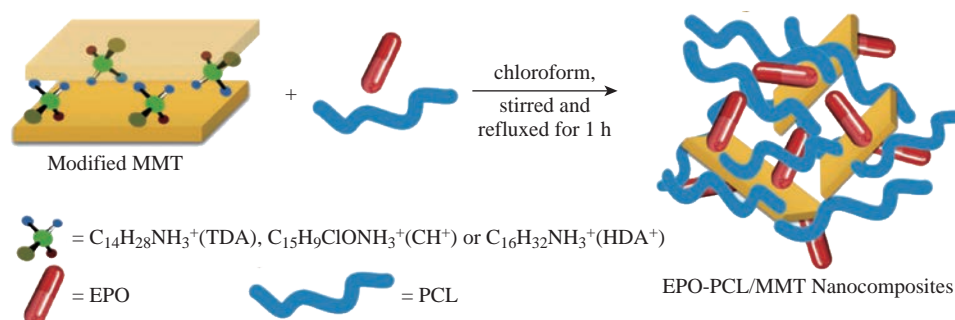

**Scheme 1** Schematic drawing of EPO-PCL/MMT nanocomposites.

## Preparation of PCL/EPO-clay nanocomposites

The required amounts of PCL and EPO were dissolved in 50 mL of chloroform, separately. The EPO solution was then transferred into the PCL solution with a dropper and continuous stirring. After all the EPO solution was transferred into the PCL solution, the resultant mixture was then stirred for 1 h. The required modified clay (CH-MMT, HDA-MMT and TDA-MMT) was then added into the dissolved PCL/EPO in the small portion. The mixture was then refluxed for 1 h and then ultrasonically stirred using the ultra sonic cathode for 10 min to make sure that the clay was fully dispersed in the PCL/EPO solution. The nanocomposite was then poured into a Petri dish and left to dry. The amounts of PCL/EPO and the modified clay used in this study are listed in Table 1.

**Table 1** Amounts of PCL/EPO and the modified clay

Sample	Weight of PBS (g)	Weight of EPO (g)	Weight of organoclay (g)
1	0.90	0.10	0
2	0.86	0.09	0.05
3	0.82	0.08	0.10
4	0.78	0.07	0.15
5	0.74	0.06	0.20
6	0.50	0.25	0.25

## Characterization

### Measurements of tensile properties

The tensile strength was measured by using Instron Universal Testing Machine 4301 at 5 mm/min of crosshead speed, in accordance with ASTM D638 [2]. Seven samples were used for the tensile test and an average of five results was taken as the resultant value.

### X-ray diffraction (XRD) analysis

X-ray diffraction (XRD) study was carried out

using Shimadzu XRD 6000 diffractometer with Cu K $\alpha$  radiation (0.15406 nm). The diffractogram was scanned in the ranges from 2° to 10° at a scan rate of 1 °/min.

### Thermogravimetric analysis (TGA)

The thermal stability of the samples was studied by using Perkin Elmer TGA 7 Thermogravimetric Analyzer. The samples were heated from 35 to 500 °C with a heating rate of 10 °C/min under a nitrogen atmosphere with a nitrogen flow rate of 20 mL/min.

### Transmission electron microscopy (TEM)

The dispersion of clay was studied by using energy filtering transmission electron microscopy (EFTEM). TEM pictures were taken in LEO 912 AB energy filtering transmission electron microscope with an acceleration voltage of 120 keV. The specimens were prepared using a Ultracut E (Reichert and Jung) cryomicrotome. Thin sections of about 100 nm were cut with a diamond knife at -120 °C.

## Results and Discussion

### Mechanical properties

The weight ratio of the PCL/EPO blend was fixed at 80:20 according to preliminary investigation which gave the highest tensile strength of the blend. Therefore, this ratio was chosen in subsequent experiments.

Table 2 shows the effect of clay content on the tensile strength properties of the PCL/EPO/HAD-modified montmorillonite (OMMT), PCL/EPO/TAD-OMMT and PCL/EPO/CH-OMMT nanocomposite. The tensile strength of the PCL/EPO blend decreased to 11.89 MPa. The addition of 0.5, 1 or 2 php of OMMT into the PCL/EPO blend increased the tensile strength. The highest tensile strength (23.23 MPa) was observed with 2 php of HAD-OMMT; tensile strength

**Table 2** Tensile properties of PCL/EPO blend, PCL/EPO/HAD-OMMT, PCL/EPO/TAD-OMMT and PCL/EPO/CH-OMMT nanocomposite


Sample	Tensile strength (MPa)		
	HAD-MMT	TAD-MMT	CH-MMT
PCL/EPO	10.79 ± 0.29	13.29 ± 0.31	10.81 ± 0.14
PCL/EPO/0.5 php OMMT	12.75 ± 0.31	14.02 ± 0.43	13.12 ± 0.32
PCL/EPO/1.0 php OMMT	17.01 ± 0.92	18.41 ± 0.72	16.05 ± 0.71
PCL/EPO/2.0 php OMMT	23.23 ± 1.25	24.15 ± 0.92	21.71 ± 0.72
PCL/EPO/3.0 php OMMT	18.98 ± 1.10	18.25 ± 0.78	17.69 ± 0.61
PCL/EPO/4.0 php OMMT	14.11 ± 0.80	14.05 ± 0.61	14.15 ± 0.49
PCL/EPO/5.0 php OMMT	10.92 ± 0.41	11.85 ± 0.56	11.61 ± 0.37

24, 15 was observed with 2 php of TAD-OMMT; and tensile strength 21.71 was observed with 2 php of CH-OMMT.

### XRD analysis

According to Bragg's law ( $n\lambda = d \sin \Theta$ ), where  $d$  refers to the distance of two consecutive clay layers, and  $\lambda$  is the wavelength of the intercept X-rays at the incident angle  $\Theta$ . The presence of CH-MMT, HDA-MMT and TDA-MMT chains in the galleries turned the original hydrophilic silicate to an organophilic silicate, and thus increased the layer-to-layer spacing of MMT [28, 29]. The interlayer distance of MMT was assigned with a basal spacing of 1.27 nm due to a  $d_{001}$  diffraction peak at  $2\Theta = 6.91^\circ$  resulted from X-ray diffraction.

The CH, HDA and TDA were treated with MMT through a cation exchange process. The cationic head groups of the intercalation agent molecule would preferentially reside at the surface layer and the aliphatic tail would radiate a ways from the surface. Fig. 1 indicates that CH, HDA and TAD were successfully intercalated into the MMT galleries. The maximum basal spacing of CH-MMT, HDA-MMT and TDA-MMT increased from 1.29 to 1.53, 1.59 and 1.79 nm, respectively (Table 3).

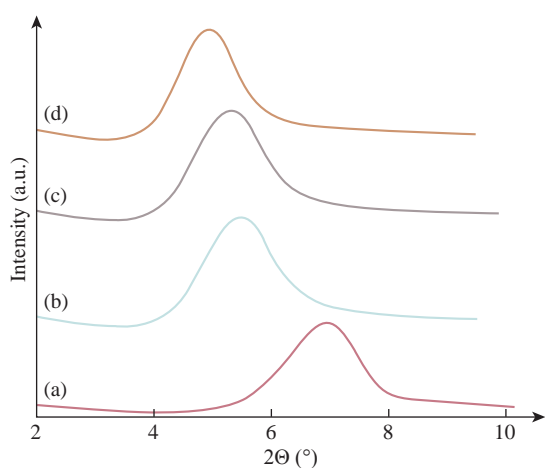


**Fig. 1** The XRD patterns of (a) MMT, (b) CH-MMT, (c) HDA-MMT, and (d) TDA-MMT.

**Table 3** Diffraction angle and basal spacing of natural clay (MMT) and modified clays with the CH-MMT, HDA-MMT and TDA-MMT

Sample	Exchanged cation	$2\Theta$ ( $^\circ$ )	D(001) spacing (nm)
MMT	$\text{Na}^+$	6.87	1.29
CH	$\text{C}_{15}\text{H}_9\text{ClONH}_3^+$ (CH <sup>+</sup> )	5.83	1.53
HAD	$\text{C}_{16}\text{H}_{32}\text{NH}_3^+$ (HDA <sup>+</sup> )	5.61	1.59
TDA	$\text{C}_{14}\text{H}_{28}\text{NH}_3^+$ (TDA)	4.92	1.79

The XRD patterns of the nanocomposites prepared by using CH, HDA and TDA (alkylammonium compounds) modified MMT nanocomposites are shown in Fig. 2. In the nanocomposites, the basal spacing of the clay increased to 2.19, 2.59 and 2.79 nm for 80PCL20EPO/CH-MMT, 80PCL20EPO/HDA-MMT and 80PCL20EPO/TDA-MMT, respectively (Table 4).

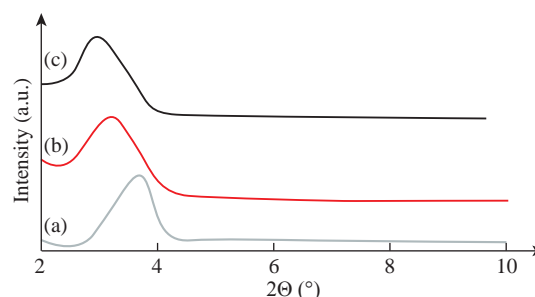

**Fig. 2** XRD patterns of (a) PCL/EPO/CH, (b) HDA and (c) TDA modified clay nanocomposites.

**Table 4** Diffraction angle and basal spacing of PLA/EPO/CH, HDA and TDA modified clay nanocomposites

Sample	$2\Theta$ ( $^\circ$ )	d-spacing (nm)
80PCL20EPO/CH-MMT	4.12	2.19
80PCL20EPO/HDA-MMT	3.41	2.59
80PCL20EPO/TDA-MMT	3.34	2.79


It was observed by Agag et al. that the basal spacing of organoclay in the polymer matrix increased with the increase in the size of the surfactant [30].

### TGA

Thermal degradation of MMT showed two steps [24]. The first one was before 200  $^\circ\text{C}$  because of the volatilization of water adsorbed on the external surfaces of the MMT and water inside the interlayer space. Decomposition of the surfactant took place in the second step between 200 and 500  $^\circ\text{C}$ .

Fig. 3 illustrates the weight loss curves (TGA) of the MMT, CH-MMT, HDA-MMT and TDA-MMT in MMT containing water due to hydrated sodium ( $\text{Na}^+$ ) cations intercalated inside the clay layers. The presence of alkylammonium groups within the MMT interlayer spacing lowered the surface energy of the inorganic structure and would transform organophobic materials to organophilic ones.

The major difference between the thermogram of the unmodified clay and that of the organoclay was that the organic constituents in the organoclay decomposed in the range from 200 to 500  $^\circ\text{C}$ , as the organic constituent in the organoclay decomposed in this range. The C decomposed as the temperature increased

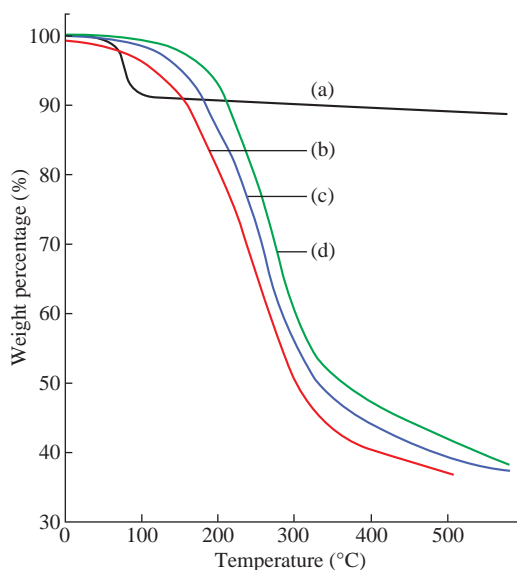

**Fig. 3** TGA of (a) Na- MMT, (b) HDA-MMT, (c) TDA-MMT and (d) CH-MMT.


from 182 to 372 °C. The decomposition process ended at 372 °C.

The CH started decomposing at higher temperatures than the TDA did, which started at 198 °C and ended at 349 °C. HDA had decomposition temperature (starting at 158 °C and ending at 308 °C). Higher decomposition temperatures of the CH-MMT, HDA-MMT and TDA-MMT were observed compared to neat MMT, which indicated that there was a strong intermolecular interaction between the alkylammonium cations and the clay.


Thermal properties were tested on PCL/EPO/HDA-MMT nanocomposites in order to determine the effect of modified clay content in the polymer matrix. The onset of the degradation of the nanocomposites was higher, i.e. 258, 261, and 267 °C for PCL/EPO containing HDA-MMT, TDA-MMT and CH-MMT, respectively, compared to the PCL/EPO blend (249 °C) (Fig. 4). The thermal stability increased with the addition of the HDA-MMT, TDA-MMT and CH -MMT. The presence of silicate layers dispersed homogeneously in the polymer sheet, hindered the permeability of volatile degradation products out from the materials and helped delay the degradation of the nanocomposites.

## TEM

Nanocomposites based materials were further analyzed by TEM technique. PCL/EPO nanocomposites modified by employing CH, HDA and TDA showed a high level of intercalation and exfoliation of the silicate layers (Fig. 5). MMT stack morphology was

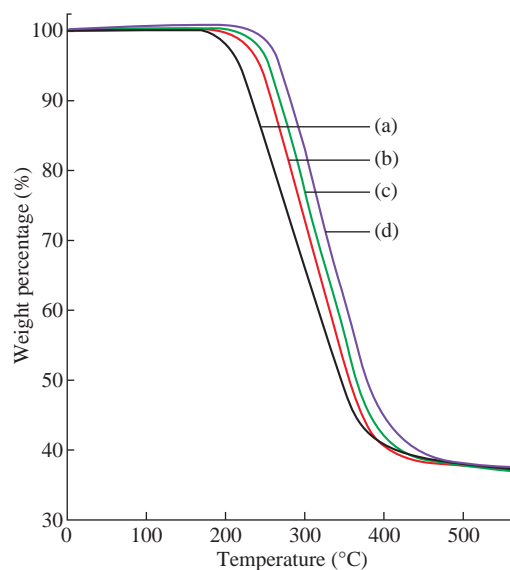

**Fig. 4** TGA thermograms of (a) PCL/EPO blends, (b) PCL/EPO/HDA-MMT, (c) PCL/EPO/TDA-MMT and (d) PCL/EPO/CH-MMT.

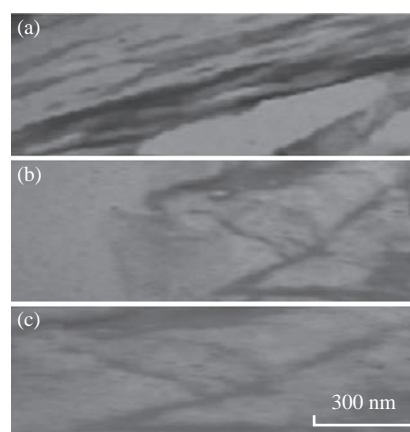

**Fig. 5** TEM of (a) PCL/EPO/HDA-MMT, (b) PCL/EPO/TDA-MMT and (c) PCL/EPO/CH-MMT nanocomposites.

fully preserved with PCL/EPO due to the incompatible nature of both constituents [27]. The dark lines represented the thickness of the individual clay layers or agglomerates.

## Conclusions

PCL/EPO modified MMT nanocomposites were prepared effectively by melt blending process. The silicate layers of the organoclay (2%) were intercalated in the polymer matrix using CH, HDA and TDA as modifiers for MMT. The formation of nanocomposites was confirmed by XRD and TEM techniques. In addition to their applications in textile industry and medical fields, biopolymer nanocomposites prepared in this study are a promising candidate

to produce disposable packaging due to their good thermal properties and processability, and potentially to be produced from renewable, biodegradable, environmental friendly and easily available raw materials.

## Conflict of Interests

The authors declare that no competing interest exists.

## References

- [1] A. Ndreu, L. Nikkola, H. Ylikaupilla, et al., Electrospun biodegradable nanofibrous mats for tissue engineering. *Nanomedicine (Lond)*, 2008, 3(1): 45-60.
- [2] E.A.J. Al-Mulla, Preparation of polylactic acid/epoxidized palm oil/fatty nitrogen compounds modified clay nanocomposites by melt blending. *Polym. Sci. Ser. A*, 2001, 53(2): 149-157.
- [3] M.M. Reddy, A.K. Mohanty, and M. Misra, Biodegradable blends from plasticized soy meal, polycaprolactone, and poly(butylene succinate). *Mac. mol. Mat. and Eng.*, 2012, 297: 455-463.
- [4] H.S. Cho, H.S. Moon, M. Kim, et al., Biodegradability and biodegradation rate of poly(caprolactone)-starch blend and poly(butylene succinate) biodegradable polymer under aerobic and anaerobic environment. *Was. Manag.*, 2010, 31: 475-480.
- [5] H. Cao, T. Liu, and Y.C. Sing, The application of nanofibrous scaffolds in neural tissue engineering. *Advanced Drug Delivery Reviews*, 2009, 61: 1055-1064.
- [6] L.L. Yu, J. Cheng, and W.L. Qu, Mechanical properties of poly(butylene succinate) (PCL) biocomposites reinforced with surface modified jute fibre. *Composites Part A: Appl. Sci. and Manuf.*, 2009, 40: 669-674.
- [7] E.A.J. Al-Mulla, W.M.Z.W. Yunus, and N.A.B. Ibrahim, Epoxidized palm oil plasticized polylactic acid/fatty nitrogen compound modified clay nanocomposites: Preparation and characterization. *Polym. and Polym. Compo.*, 2010, 18: 451-459.
- [8] B.J. Pfister, T. Gordon, Biomedical engineering strategies for peripheral nerve repair: Surgical applications, state of the art, and future challenges. *Critical Reviews™ in Biomedical Engineering*, 2011, 39(2): 81-124.
- [9] E.A.J. Al-Mulla, W.M.Z.W. Yunus, and N.A.B. Ibrahim, Properties of epoxidized palm oil plasticized polylactic acid. *J. Mat. Sci.*, 2010, 45: 1942-1946.
- [10] E.A.J. Al-Mulla, Preparation of new polymer nanocomposites based on poly (lactic acid)/fatty nitrogen compounds modified clay by a solution casting process. *Fib. Polym.*, 2011, 12 (4): 444-450.
- [11] E.A.J. Al-Mulla, Polylactic acid/epoxidized palm oil/fatty nitrogen compounds modified clay nanocomposites: preparation and characterization. *Kor. J. Chem. Eng.*, 2011, 28(2): 620-626.
- [12] M.M. Radhi, E.A.J. Al-Mulla, Use of a grafted polymer electrode to study mercury ions by cyclic voltammetry. *Res. Chem. Inter.*, 2015, 4: 1413-1420.
- [13] F.A. Shemmari, A.A.A. Rabah, Comparative study of different surfactants for natural rubber clay nanocomposite preparation. *Rendiconti Lincei.*, 2014, 25: 409-413.
- [14] M. Dadsetan, H. Mirzadeh, N. Sharifi Sanjani, et al., Cell behavior on laser surface-modified PET in vitro. *J. Biomed. Mater. Res.*, 2001, 57: 183-189.
- [15] T. Yokohara, M. Yamaguchi, Structure and properties for biomass based polyester blends of PLA and PCL. *Eur. Polym. J.*, 2008, 44:677-685.
- [16] D.J. Kim, W.S. Kim, and D.H. Lee, Modification of Poly(butylene succinate) with Peroxide: Crosslinking, Physical and Thermal Properties, and Biodegradation. *J. Appl. Polym. Sci.*, 2001, 81 5: 1115-1124.
- [17] M.G. Al-Mosawy, E.A.J. and Al-Mulla, M.J. Mohamad, Bentonite-based nano organic clay using chalcone and azo dye as organophilic reagents. *Nano Biomed. Eng.*, 2017, 9(2): 124-128.
- [18] E.A.J. Al-Mulla, W.M.Z.W. Yunus, and N.A.B. Ibrahim, Di fatty acyl urea from corn oil: synthesis and characterization. *J. Ole. Sci.*, 2010, 59: 157-161.
- [19] Z. Kulinski, E. Piorkowska, Crystallization, structure and properties of plasticized poly(l-lactide). *Polyme*, 2005, 46: 10290-10300.
- [20] Z. Ren, L. Dong, and Y. Yang, Dynamic mechanical and thermal properties of plasticized poly(lactic acid). *J. Appl. Polym. Sci.*, 2006, 101: 1583-1590.
- [21] E.P. Giannelis, Polymer-layered silicate nanocomposites: synthesis, properties and applications. *Appl. Organomet. Chem.*, 1998, 12: 675-680.
- [22] M. Radhi, Z. Hamed, and S. Ezzaldeen, Effect of micro- and nanoparticles of ampicillin trihydrate on blood medium: A voltammetric study. *Nano Biomed. Eng.*, 2017, 9(3): 185-190.
- [23] E.P. Giannelis, R. Krishnamoorti, and E. Manias, Polymer-silicate nanocomposites model systems for confined polymers and polymer brushes. *Adv. Polym. Sci.*, 1999, 138: 107-143.
- [24] M. Arroyo, M. Lopez-Manchado, and B. Herrero, Organo-MMT as substitute of carbon black in natural rubber compounds. *Polymer*, 2003, 44: 2447-2453.
- [25] M.A. Paul, M. Alexandre, P. Degée, et al., Nanocomposite materials based on plasticized poly(l-lactide) and organomodified MMT: Thermal and morphological study. *Polymer*, 2003, 44: 443-450.
- [26] S.A. Sadiq, E.M. Atiyah, and A.T. Numan, Synthesis and characterization of new bidentate chalcone ligand type (NO) and its MnII, CoII, NiII and CuII complexes with study of their antibacterial activity. *Diyala J. Pure Sci.*, 2015, 11(3): 2222-8373
- [27] E.A.J. Al-Mulla, A.H. Suhail, and A.A. Saadon. New biopolymer nanocomposites based on epoxidized soybean oil plasticized poly(lactic acid)/fatty nitrogen compounds modified clay: Preparation and characterization. *Indust. Crops Prod.*, 2011, 33: 23-29.
- [28] Z. Ren, L. Dong, and Y. Yang, Dynamic mechanical and thermal properties of plasticized poly(lactic acid). *J. Appl. Polym. Sci.*, 2006, 101: 1583-1590.
- [29] F. Chen, P. Huang, and X.M. Mo, Electrospinning of heparin encapsulated P(LLA-CL) core/shell nanofibers. *Nano Biomed. Eng.*, 2010, 2: 56-60.
- [30] T. Agag, T. Takeichi, Polybenzoxazine-MMT hybrid nanocomposites: synthesis and characterization. *Polymer*, 2000, 41: 7083-7089.
- [31] E.A.J. Al-Mulla, W.M.Z. Yunus, N.A. Ibrahim, et al., Synthesis and characterization of N,N-carbonyl difatty

- amide from palm oil. *J. Oleo Sci.*, 2009, 58: 467-471.
- [32] E.A.J. Al-Mulla, A new biopolymer-based polycaprolactone/starch modified clay nanocomposite. *Cellulose Chem. Technol.*, 2014, 48 (5-6): 515-520.
- [33] W.H. Hoidy, M.B. Ahmad, and E.A.J. Al-Mulla, Synthesis and characterization of fatty hydroxamic acids from triacylglycerides. *J. Ole. Sci.*, 2010, 59: 15-19.

**Copyright**© 2017 Emad Abbas Jaffar Al-Mulla, Fayq Hsan Jabbar, Zaidoon Jawad Kadhim, Ali Abdulabbas Abdullah, Ahmed Ghanim Wadday, and Sabah Mohammed Mlkat. This is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.